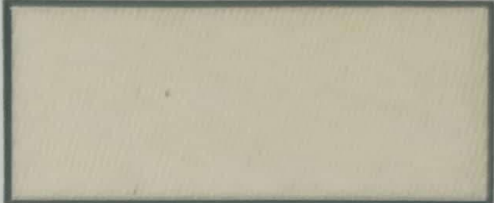
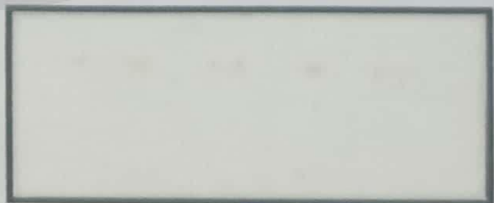
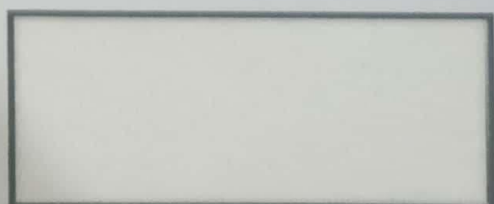


LAMPIRAN 1

KAIN HASIL PENELITIAN

Tabel 1.1 Lampiran Kain Hasil Penelitian

Konsentrasi Zat pembantu tekstil multifungsi (N23B-425) g/L	Kain Hasil Pemasakan dan Pengelantangan Simultan
Greige	
Standar	
1	
2	
3	
4	

LAMPIRAN 2

DATA HASIL PENGUJIAN KAIN CONTOH UJI

Tabel L 2. 1 Data Daya Serap Uji Tetes

Konsentrasi Zat pembantu tekstil multifungsi (N23B-425) g/L	Nilai DS (detik)	Rata-rata DS (detik)
<i>Greige</i>	21	20
	20	
	21	
	19	
	19	
Standar	3,84	3,65
	3,78	
	3,23	
	3,67	
	3,74	
1	9,14	9,74
	9,87	
	9,92	
	9,90	
	9,89	
2	5,75	5,45
	5,19	
	5,71	
	5,25	
	5,33	
3	1,82	1,66
	1,65	
	1,75	
	1,75	
	1,34	
4	0,88	0,84
	0,72	
	0,84	
	0,87	
	0,87	

Tabel L 2. 2 Data Daya Serap Uji Kapilaritas Tekstil

Konsentrasi Zat pembantu tekstil multifungsi (N23B-425) g/L	Nilai DS (cm)	Rata-rata DS (cm)
Greige	0,6	0,6
	0,6	
	0,6	
	0,6	
	0,6	
Standar	8,5	8,6
	8,2	
	8,5	
	8,9	
	8,9	
1	3	2,9
	2,8	
	3,1	
	2,5	
	3,1	
2	5,9	6,68
	7,9	
	6,9	
	5,9	
	6,8	
3	10,8	11,06
	10,9	
	11,1	
	11	
	11,5	
4	12,1	12,1
	12,3	
	11,8	
	11,5	
	12,8	

Tabel L 2. 3 Data Derajat Putih

Konsentrasi Zat pembantu tekstil multifungsi (N23B-425) g/L	Nilai Derajat Putih (%)	Rata-rata Derajat Putih (%)
Greige	1,25	1,13
	1,08	
	1,12	
	1,17	
	1,06	
Standar	78,51	78,56
	79,24	
	78,97	
	78,34	
	77,76	
1	67,31	67,77
	67,01	
	68,02	
	68,31	
	68,18	
2	68,22	68,73
	68,53	
	69,35	
	68,63	
	68,93	
3	79,07	79,08
	79,33	
	78,66	
	79,40	
	78,94	
4	80,41	80,11
	79,70	
	80,21	
	80,60	
	79,61	

Tabel L 2. 4 Data Kekuatan Jebol

Konsentrasi Zat pembantu tekstil multifungsi (N23B-425) g/L	Nilai Kekuatan Jebol (kg/cm ²)	Rata-rata Kekuatan Jebol (kg/cm ²)
Greige	6,59	6,14
	6,34	
	6,85	
	5,58	
	5,35	
Standar	4,87	5,17
	4,81	
	5,49	
	5,16	
	5,56	
1	5,5	5,30
	5,48	
	5,33	
	5,02	
	5,19	
2	5,36	5,23
	4,79	
	5,47	
	5,71	
	4,85	
3	5,10	5,12
	5,15	
	5,23	
	5,09	
	5,04	
4	5,28	5,01
	5,48	
	4,92	
	5,31	
	4,09	