

LAMPIRAN

Lampiran 1 Hasil Data Pengujian CPI

CPI		
No	Sampel 1	variasi kain 2
1	35	33
2	33	35
3	33	34
4	35	33
5	34	35
6	34	35
7	35	32
8	32	34
9	30	34
10	33	35
AVERAGE	33,40	34,00
STD DEVASI	1,58	1,05
CV	4,48%	2,94%

Lampiran 2 Hasil Data Pengujian WPI

WPI		
No	variasi kain 1	variasi kain 2
1	25	26
2	26	25
3	25	26
4	25	27
5	26	28
6	28	28
7	27	27
8	26	25
9	26	25
10	28	27
AVERAGE	26,20	26,40
STD DEVASI	1,14	1,17
CV	4,11%	4,22%

Lampiran 3 Hasil Data Pengujian Thickness

THICKNESS		
No	variasi kain 1	variasi kain 2
1	0,53	0,73
2	0,59	0,73
3	0,52	0,7
4	0,56	0,79
5	0,51	0,78
6	0,53	0,73
7	0,54	0,7
8	0,53	0,73
9	0,55	0,74
10	0,56	0,74
AVERAGE	0,54	0,74
STD DEVASI	0,02	0,03
CV	4,11%	3,94%

Lampiran 4 Hasil Data Pengujian Gramasi

GRAMASI		
No	variasi kain 1	variasi kain 2
1	170,6	293,5
2	170,2	293,4
3	170.4	293,6
AVERAGE	170,40	293,50
STD DEVASI	0,28	0,10
CV	0,12%	0,03%



Lampiran 5 Pengujian DTU Kain 2

/ST3 cm kubik_POLRAY_00154_20240522_152848.pnt.xml	
Instrument:	FX 5500 LabAir IV
Serial Number:	154
Settings	
Test pressure:	100 Pa
Test area:	20 cm ²
Nom / Min / Max:	-1.00 / -1.00 / -1.00 cm ³ /cm ² /s
Statistical analysis	
Average:	156 cm ³ /cm ² /s
Minimum:	146 cm ³ /cm ² /s
Maximum:	165 cm ³ /cm ² /s
CV:	3.98 %
Cpk:	0.0000
Test results	
1	157 cm ³ /cm ² /s
2	153 cm ³ /cm ² /s
3	154 cm ³ /cm ² /s
4	163 cm ³ /cm ² /s
5	146 cm ³ /cm ² /s
6	147 cm ³ /cm ² /s
7	157 cm ³ /cm ² /s
8	164 cm ³ /cm ² /s
9	153 cm ³ /cm ² /s
10	165 cm ³ /cm ² /s

Lampiran 6 Pengujian DTU Kain 1

Date:	22.05.2024
Time:	15:14:09
Instrument:	FX 3300 LabAir IV
Serial Number:	154


Settings	
Test pressure:	100 Pa
Test area:	20 cm ²
Nom / Min / Max:	-1.00 / -1.00 / -1.00 cm ³ /cm ² /s

Statistical analysis	
Average:	256 cm ³ /cm ² /s
Minimum:	222 cm ³ /cm ² /s
Maximum:	285 cm ³ /cm ² /s
CV:	7.59 %
Cpk:	0.0000


Test results	
1	222 cm ³ /cm ² /s
2	230 cm ³ /cm ² /s
3	240 cm ³ /cm ² /s
4	275 cm ³ /cm ² /s
5	255 cm ³ /cm ² /s
6	276 cm ³ /cm ² /s
7	260 cm ³ /cm ² /s
8	260 cm ³ /cm ² /s
9	285 cm ³ /cm ² /s
10	255 cm ³ /cm ² /s

us Highlight all Match case


Lampiran 7 Water Location MMT Kain 1

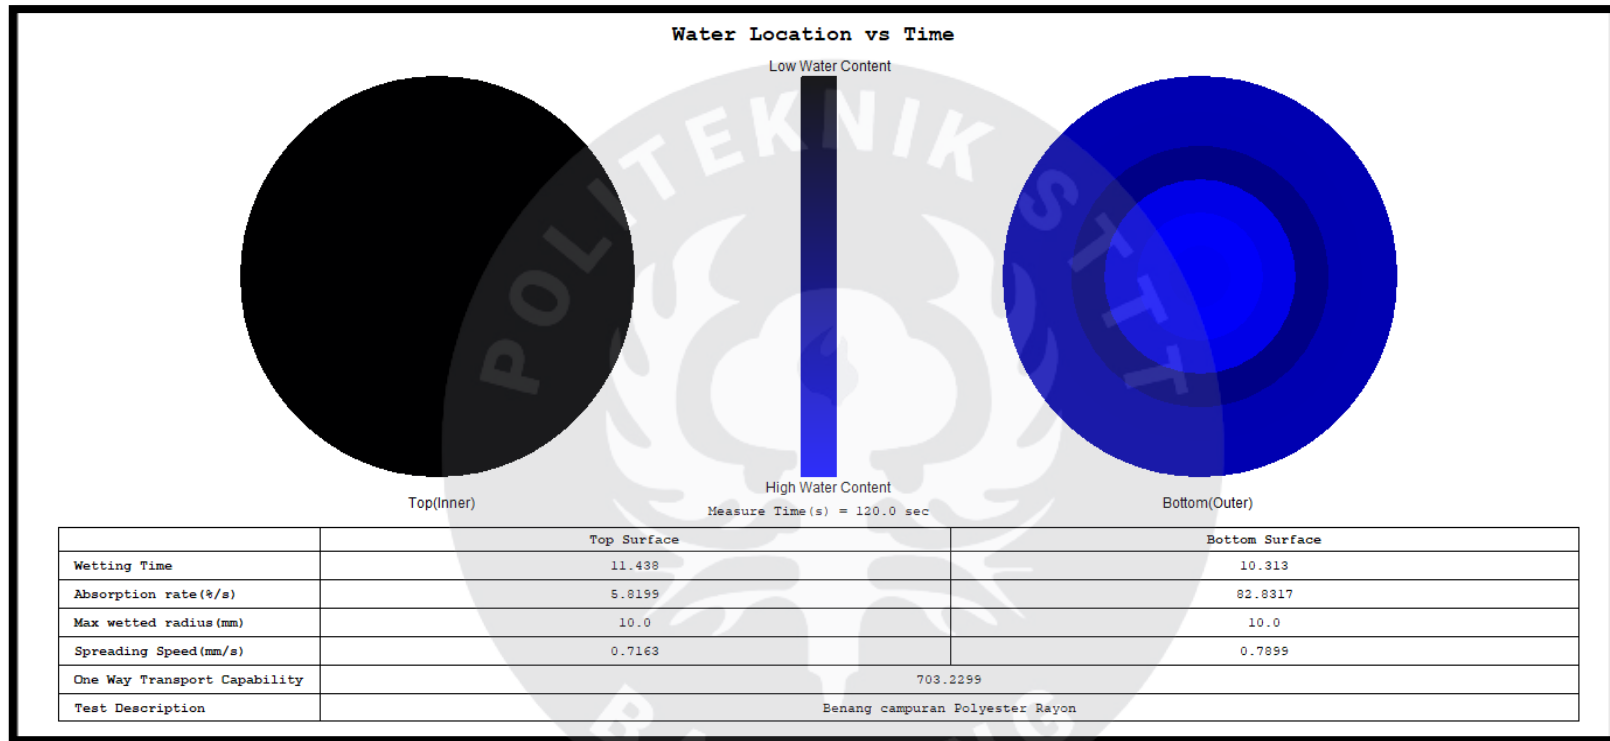


Lampiran 8 Water Content MMT Kain 1

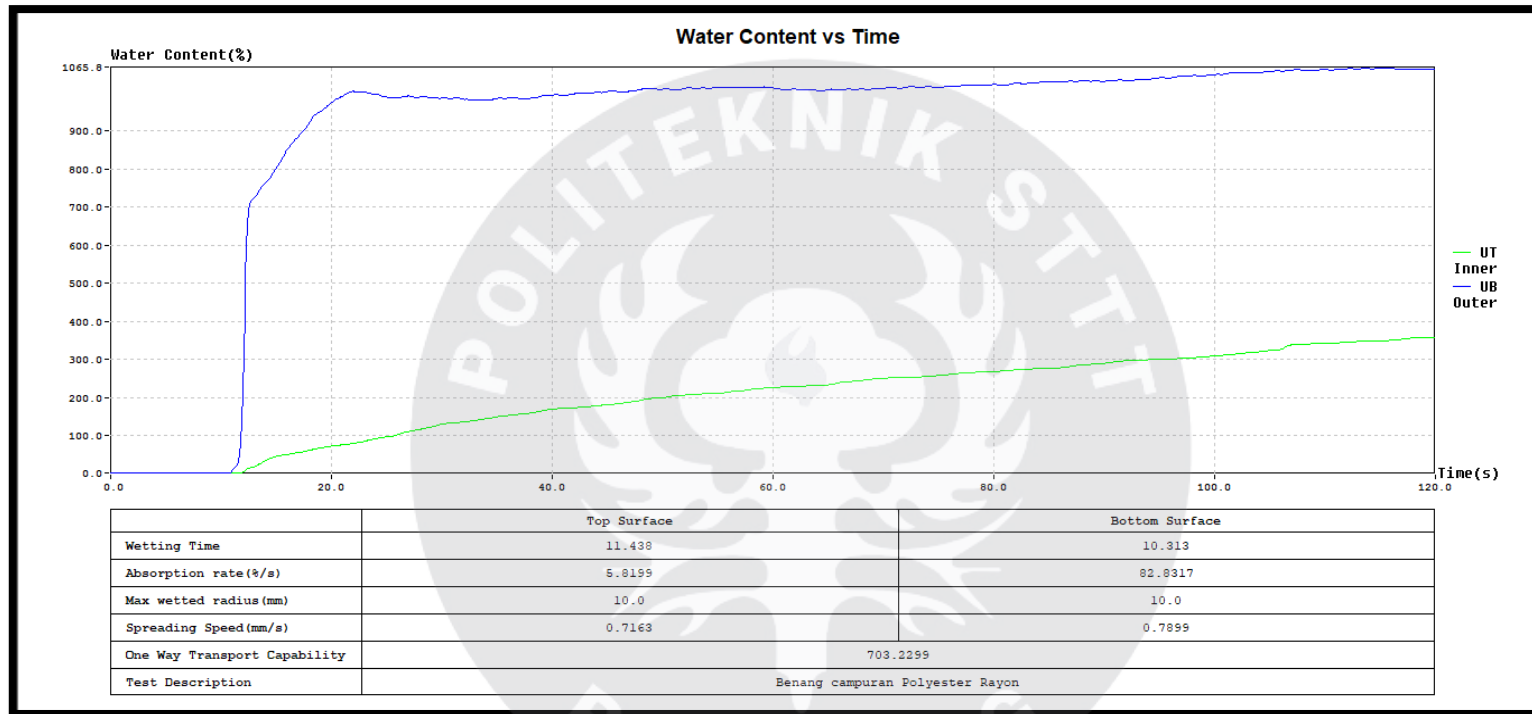


Lampiran 9 AATCC MMT Kain 1

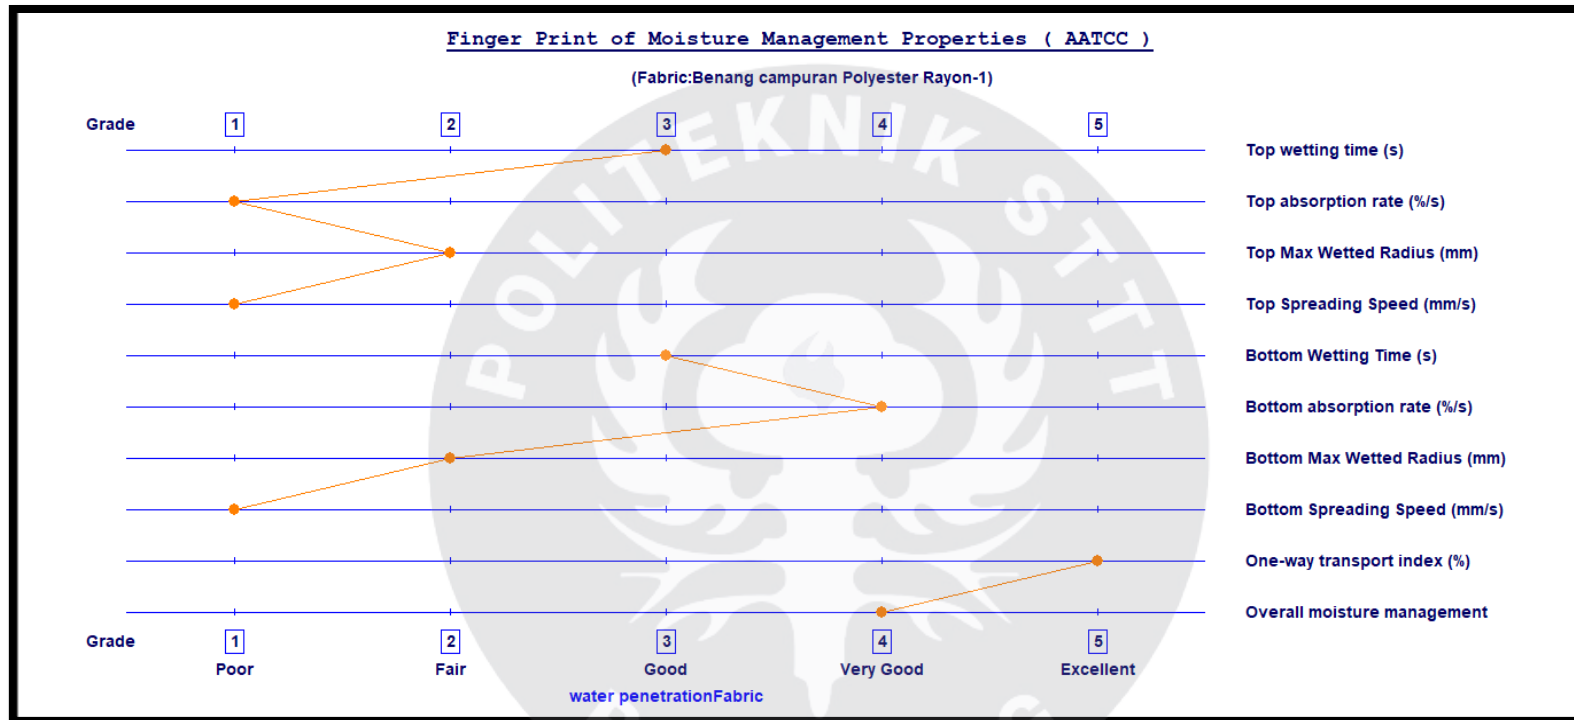


Lampiran 10 Water Location Kain 2

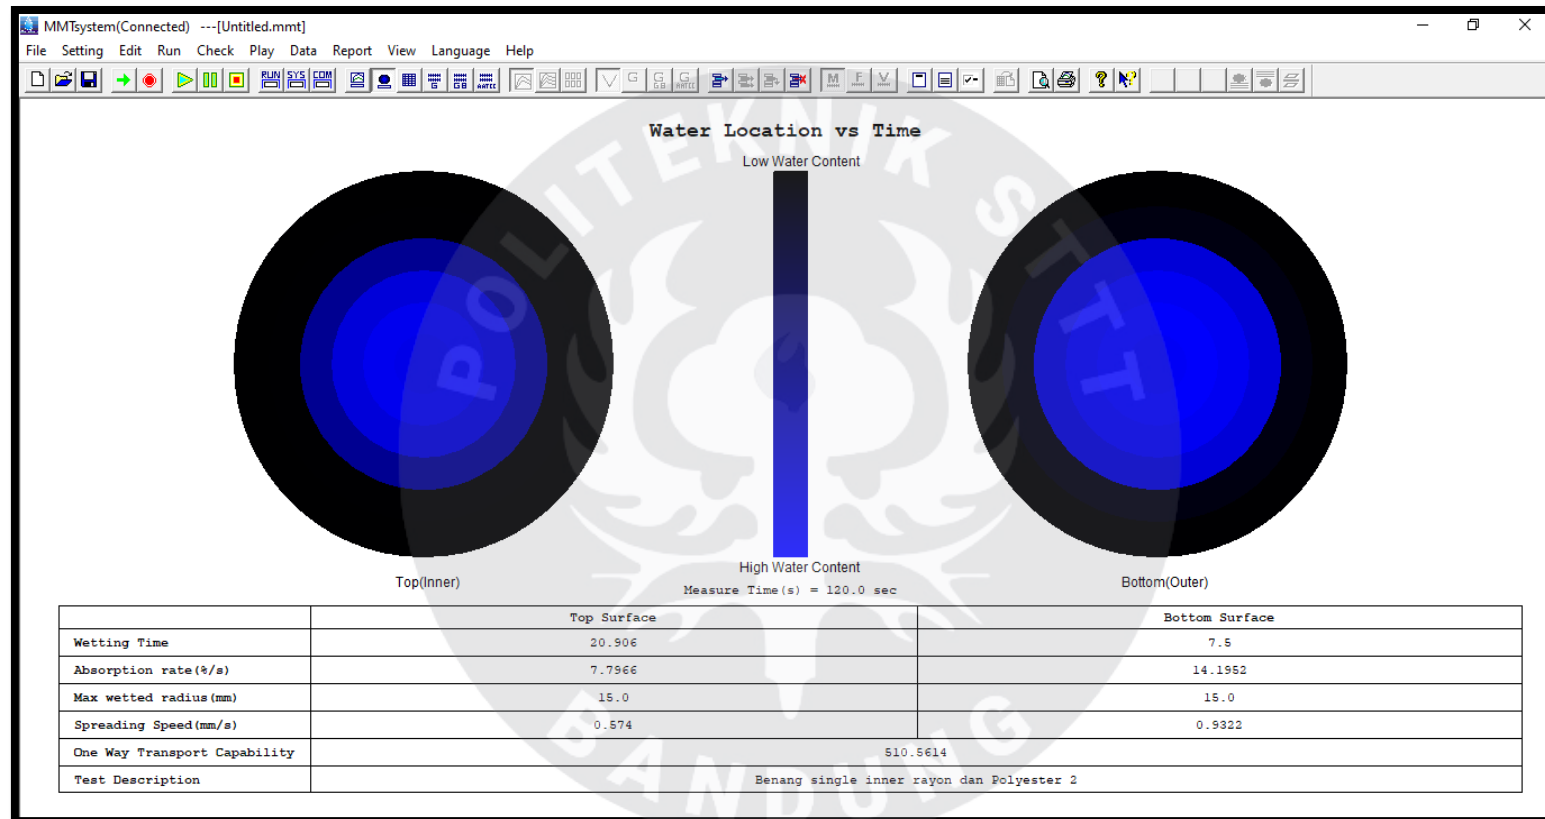

Lampiran 11 Water Content Kain 2

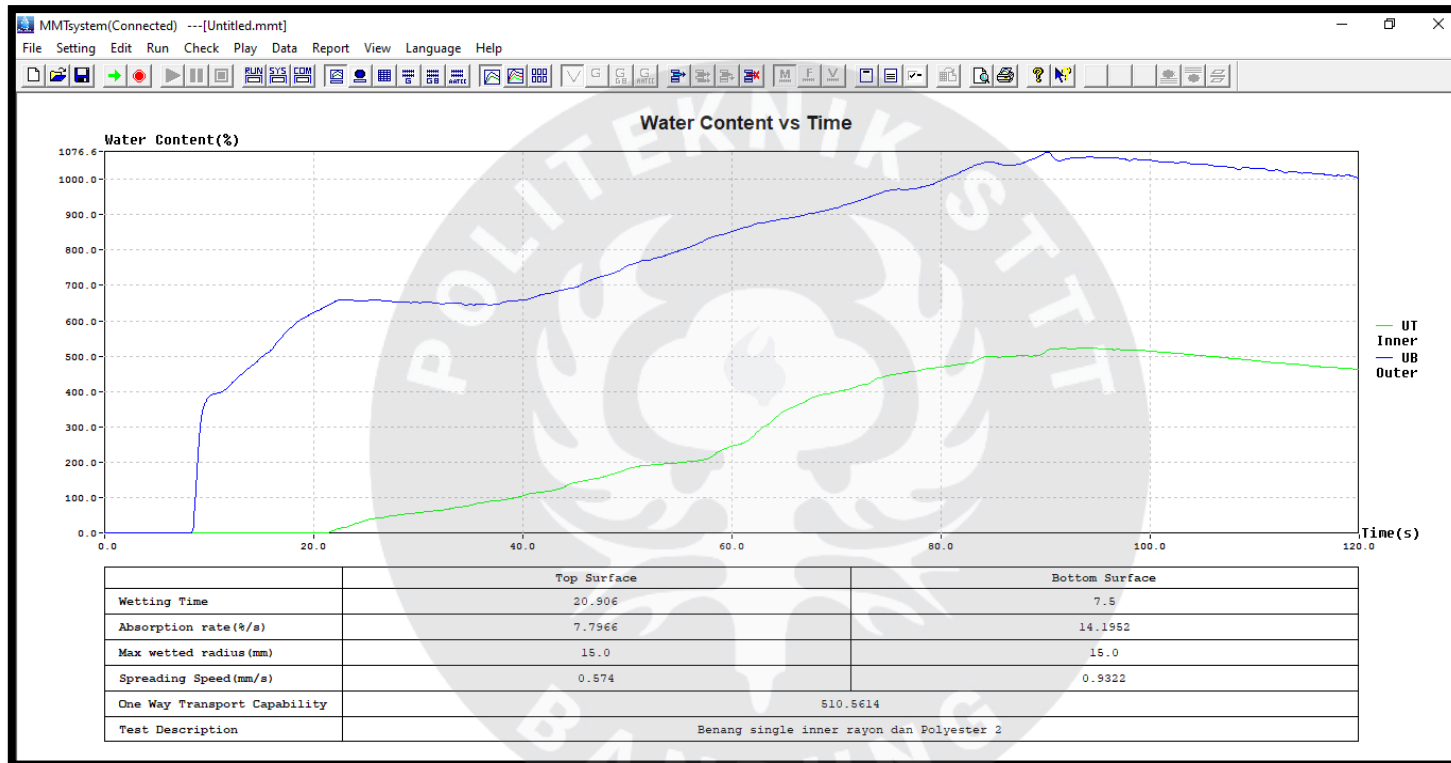

Lampiran 12 AATCC MMT Kain 2

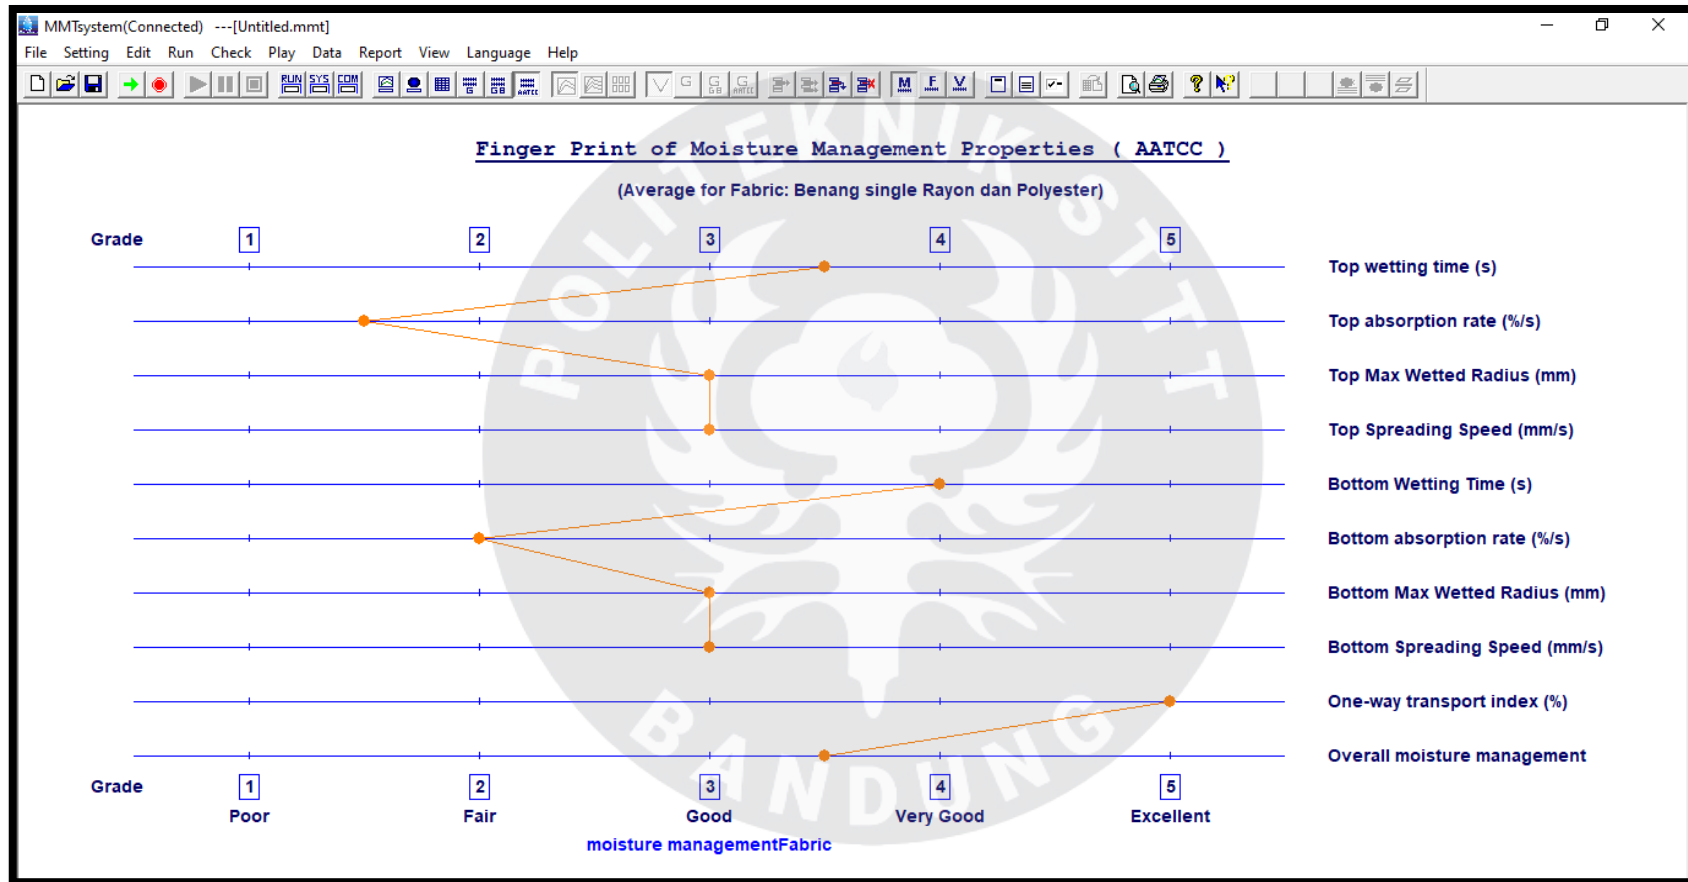

Lampiran 13 Uji larutan kimia

